

**Mechanical Characterization of 37 Micron Sized B₄C Particulates Reinforced
Al7475 Alloy Composites**Prashanth A N^{1*}, P Selvaraj², Madeva Nagaral³

^{1*} *Research Scholar, Aeronautical Development Agency, Bangalore-560037 & Chief Manager, Aircraft Research and Design Centre, HAL, Bangalore-560037*

² *Scientist, Aeronautical development Agency, Bangalore-560037*

³ *Design Engineer, Aircraft Research and Design Centre, HAL, Bangalore-560037*

Abstract:- *In the current study, an investigation made on fabrication of 37 micron B₄C particles reinforced Al7475 alloy composites and evaluation of mechanical properties. Al7475-2, 4 and 6 wt. % of B₄C composites were synthesized by liquid stir casting process. Microstructural characterization was carried out by using scanning electron microscope and energy dispersive spectroscope. Prepared composites were evaluated for mechanical properties as per ASTM standards. Scanning electron micro photographs revealed the distribution of B₄C particulates in the Al matrix and were confirmed by EDS analysis. Further, B₄C particulates reinforced composites were shown more enhanced hardness, ultimate tensile strength and yield strength as compared to Al7475 alloy. Ductility of Al7475 alloy was decreased with addition hard ceramic particles.*

Keywords: *Al7475 Alloy, B₄C particulates, Microstructure, Hardness, Tensile Strength*

I. INTRODUCTION

Aluminum is the most bottomless material in the earth. Aluminum amalgams are utilized as a principle metal framework component in the composite materials [1]. Aluminum combinations are utilized in car, marine, aviation, gadgets, barrier and sports divisions because of having light in weight, high quality, malleability and erosion opposition. In any case, aluminum compounds have low wear obstruction. Distinctive fortifications are added to the aluminum combinations to enhance the wear obstruction. The fortifications are added with the aluminum amalgam to frame aluminum metal framework composites. The aluminum metal lattice composites have high rigidity, high hardness light in weight and erosion opposition over the un strengthened aluminum compounds. The fortifications added to the aluminum combinations are three sorts 1. Engineered clay fortification 2. Industrial disperse materials utilized as fortifications and 3. Agro disseminate material utilized as support. Engineered fortifications are Al₂O₃, SiC, TiC, SiO₂, BN, B₄C, MgO, ZrB₂. These are costly fortifications and with restricted accessibility [2-3]. The Manufacturing cost of aluminum compounds fortified with clay support is high, because of surprising expense of ceramic fortification.

Aluminium-based metal matrix composites (MMCs) reinforced with ceramic particles is interesting structural and functional materials. They have been found in a wide range of applications in automotive and aerospace industries because of their lightweight, high stiffness and strength, high thermal stability and their superior wear resistance, compared to the unreinforced aluminium alloys [4, 5].

Particulate strengthened metal matrix composites (PMMC), established of high-quality metallic combinations fortified with artistic particulates or whiskers, are propelled materials that have risen up out of the ceaseless need of lighter-weight, higher-execution segments in the aviation, flying machine and all the more as of late the car businesses. For sure, these "new" materials offer promising points of view in helping car specialists to accomplish enhancement in vehicle eco-friendliness. Their particular properties of high firmness, high quality and low thickness have advanced an expanding number of uses for these materials. A few of these applications require improved rubbing and wear exhibitions, for instance brake rotors, motor engine blocks and chamber liners, associating pole and cylinder, gears, valves, pulleys, suspension parts, and so on [6, 7].

Recently, B₄C reinforced composites have been manufactured via various techniques. B₄C is the third hardest material after diamond and cubic boron nitride (CBN). Furthermore, B₄C has a lower specific gravity (2.51 g/cm³, which is less than that of Al with 2.8 g/cm³), high wear and impact resistance, high melting point, good resistance to chemical agents and high capacity for neutron absorption. B₄C is a proper candidate as reinforcement in Al matrix composites. It can be considered as an alternative to SiC reinforced composites, where a high stiffness or a good wear resistance is required.

Among various techniques to fabricate metal matrix composites (MMCs) reinforced with ceramic particles, stir casting is one of acceptable routes for commercial production. However, this method needs delicate optimization of parameters like casting temperature, stirring velocity, reinforcement content. In as-cast AMCs, inferior ductility limits their

performance and applications. Parameters like matrix microstructure, distribution of reinforcements, porosity content affect the ductility [8, 9].

In this research, composites with 37 micron sized B₄C content as reinforcement were fabricated via stir casting. The aluminum-micro B₄C composites play an important role in the industry because of the increase demand of advanced light weight materials in different industrial applications. Keeping the above observations in view, it is proposed to develop Al7475 composites with 2, 4 and 6 wt. % of B₄C particulates.

II. EXPERIMENTAL DETAILS

Table 1- Chemical Composition of Al7475 alloy by weight%

Zn	Mg	Si	Fe	Cu	Ni	Mn	Cr	Al
0.1	1.8	0.2	1.3	2.7	0.9	0.3	0.1	Balance

The aluminum alloys are basically classified into two categories these are cast aluminum and wrought aluminum. In the present research work Al7475 alloy is used as the matrix material which is one type of wrought aluminium alloy designated by 4 numbers, having zinc as the primary element and combined with various other elements like copper, magnesium, silicon and many more elements which are listed in chemical composition of Table 1. 660 °C is the melting point of Al7475 alloy is and the density is 2.84 g/cc.

Boron Carbide is one of the hardest man-made materials available in commercial quantities. Boron carbide ceramics have excellent physical and mechanical properties, such as a high melting point, hardness, good abrasion resistance, high impact resistance and excellent resistance towards corrosion. As an outstanding in borne mechanical property, the boron carbide as a ceramic material have attracted attention over wide variety of applications that comprises light-weight armour plating, blasting nozzles, mechanical seal faces, grinding tools, cutting tools and neutron absorption materials.

37 micron ceramic B₄C particles were used as the reinforcement in the Al7475 alloy base matrix. Micro composites were produced by simplest and most economical used technique known as stir casting technique or vortex technique. Al7475 alloy is heated to the temperature of 750°C in electrical resistance furnace. Thermocouple is used to check the temperature of the melt in the graphite crucible. At around 750°C, powder of hexa-chloroethane (C₂Cl₆) is added to the melt to remove all the unwanted trapped gasses and thus prevents casting defects like blow holes and porosity. Next, magnesium was added to decrease the surface tension and viscosity of the melt. The required quantities of preheated B₄C were taken in separate containers and added to Al7475 melt with continuous stirring for about 5-6 minutes at 300-350 rpm by zirconium-coated stirrer until a clear vortex is formed leading to good bonding, increase in the wettability between matrix and reinforced particles and to avoid agglomeration aimed at obtaining uniform homogenous distribution of reinforced particulates in the melt.

After mixing of the reinforcement particulates, the temperature of the melt reduced and started to solidify following which the melt was superheated above the liquid temperature with continued stirring and finally poured into permanent mould made of cast iron and allowed to solidify. After complete solidification, the casting is removed from the mould. Composites thus prepared were machined according to the ASTM standards. Now the Al7475-2, 4 and 6 wt.% of B₄C composite samples were subjected to various tests. Samples were tested for microstructural characterization by using Scanning Electron Microscope (SEM) and Energy Dispersive Spectroscopy (EDS). Mechanical behavior like hardness, ultimate tensile strength and yield strength were evaluated as per ASTM standards.

III. RESULTS AND DISCUSSION

To examine SEM images, the samples were preferred from the middle segment from the cylindrical specimens. Fig. 1a-c shows the SEM microstructure of as cast Al7475 alloy and the composite of 2, 4 and 6 wt. % of B₄C reinforced with Al7475 alloy. The microstructure of as cast Al7475 alloy comprises of fine grains of solid solution of the aluminium along with an ample distribution of inter-metallic precipitates. In additionally, the prepared micro composite shows the great bonding among the framework and the reinforcement alongside the uniform homogenous circulation of estimated B₄C particulates without any agglomeration and bunching in the composites. This is essentially because of the practical mixing activity accomplished all through by two stage addition process of 37 micron sized B₄C. By the uniform distribution of micro particle in matrix, the grain limit of the lattice obstructs the grain improvement and opposes the separation development of grains amid stacking.



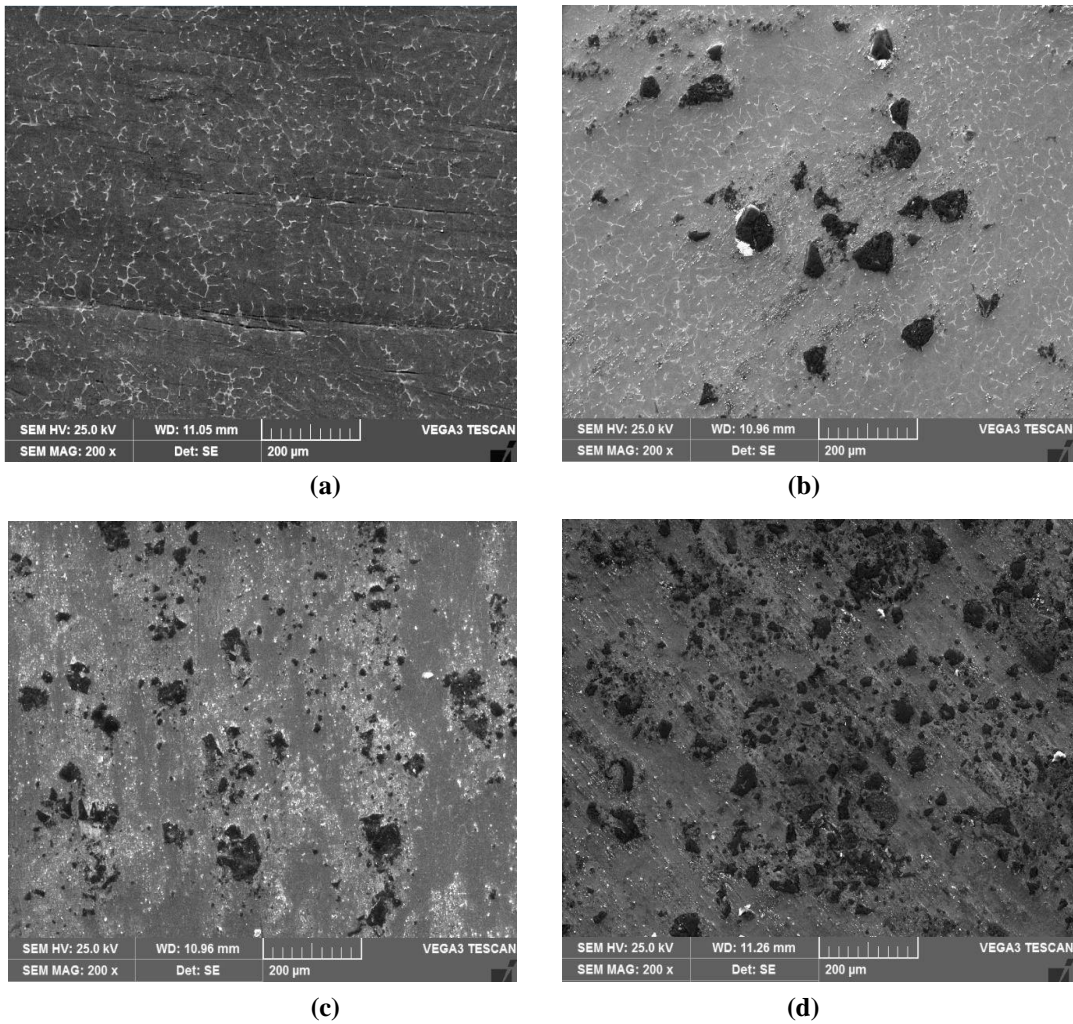


Figure 1: SEM micrographs of (a) as cast Al7475 alloy (b) Al7475-2 wt.% B₄C (c) Al7475-4 wt.% B₄C (d) Al7475-6 wt.% B₄C (37 micron) composites

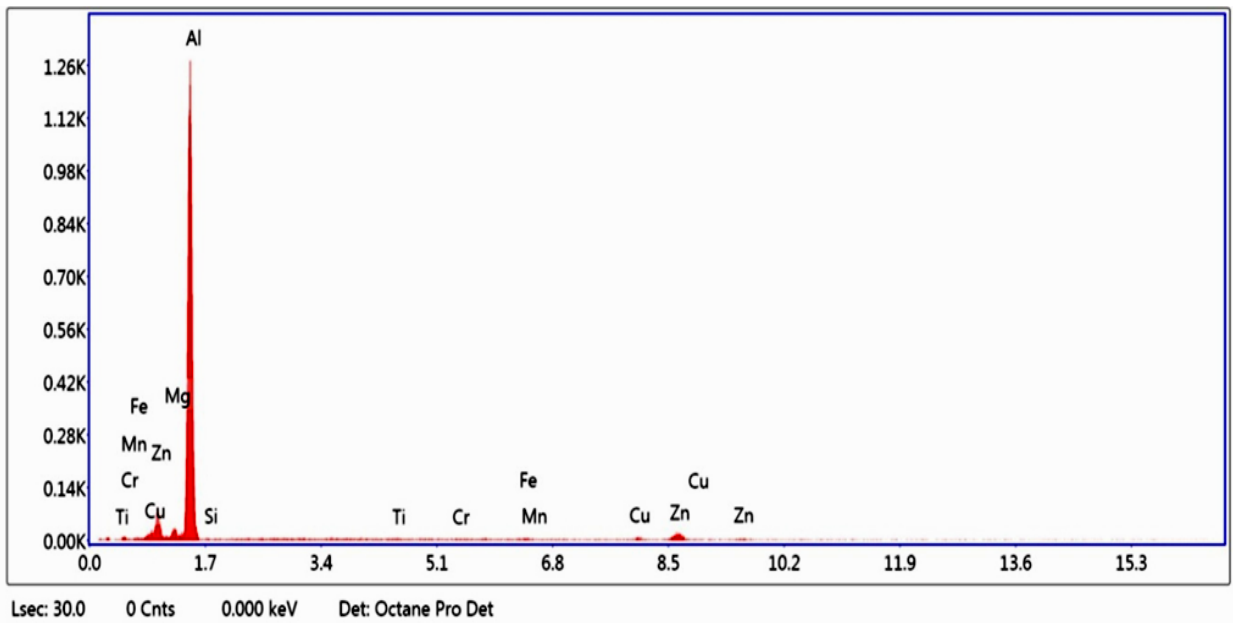

(a)

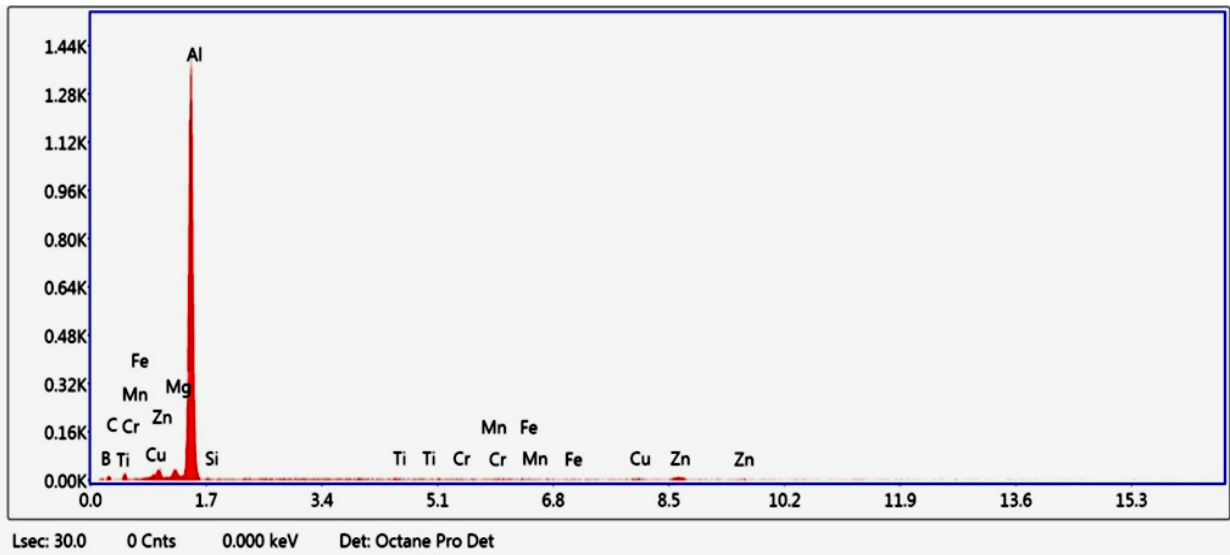

(b)

Figure 2: Showing energy dispersive spectrum analysis of (a) Al7475 alloy and (b) Al7475-6wt. % 37 micron B_4C composite

Energy dispersive spectrum analysis (fig.2b) confirmed the presence of micro B_4C particulates in the form of B and C elements in the Al7475 alloy base matrix.

Hardness Measurements

The hardness is a mechanical parameter demonstrating the capability of resisting of prepared materials to indentation under a static load. The variation in the hardness can be observed from figure 3 with the addition of 2, 4 and 6 wt. % of 37 micron B_4C particulates to the Al7475 alloy with respect to unreinforced alloy. The increase is observed from 63.4 BHN to 94.9 BHN for Al7475-6 wt.% of B_4C composites. This can be credited to the because of the of harder B_4C particles in the lattice than base alloy, and the higher constraint to the localized matrix deformation during indentation as an outcome of the presence of harder phase [10]. Furthermore the B_4C , as other fortifications fortifies the matrix by making of high density dislocations amid cooling to room temperature because of the distinction of coefficients of thermal expansion developments between the micro B_4C and grid Al7475 compound. The mismatch strains developed between the micro reinforcement and the matrix obstructs the movement of dislocations, by resulting in the improvement of the hardness of the prepared nano composites [11]

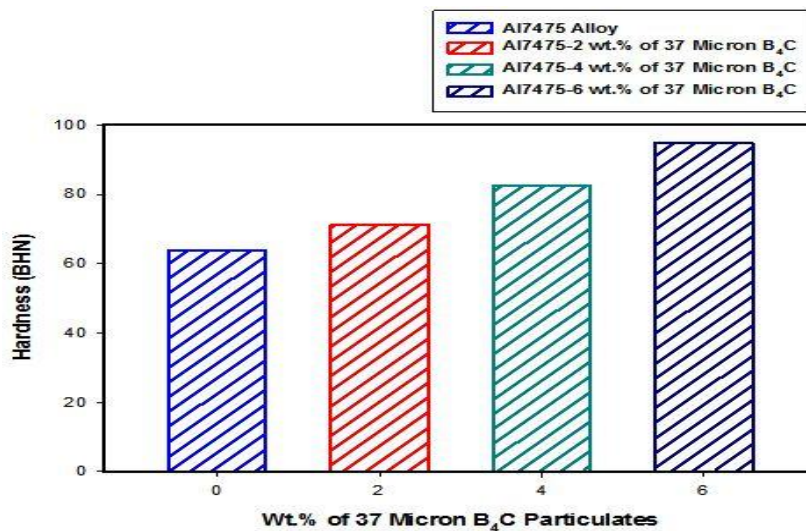


Figure 3: Hardness of Al7475 alloy and 37 micron size B_4C composites Ultimate Tensile Strength and Yield Strength

Figure 4 represents the plot of ultimate tensile strength (UTS) with 2, 4 and 6 wt. % of 37 micron B_4C dispersoids in metal lattice composite. As a component of weight rate of B_4C particles the calculated estimations of ultimate tensile strength were plotted. When compared to base Al7475 alloy with 2, 4 and 6 wt.% of B_4C composites, there has been a increase of

12.9%, 21.1% and 32.7% in UTS respectively. The major increase in strength is credited because of legal contact between the framework mixture and the supporting materials. Better the grains estimate better is the hardness and additionally the better quality of composites prompting to enhance the wear resistance [12]. The improvement in UTS is credited by the hard micro ceramic B_4C particulates, which confers quality to the framework mixture, in this way giving improved solid rigidity. The expansion of these hard B_4C particles may have offered rise to huge lasting compressive unease created along with cementing because of contrast in coefficient of developed between flexible matrix and brittle particles. The improvements of quality are likewise attributed to closer packing of reinforcement and thus little inter particle spacing in the lattice [13].

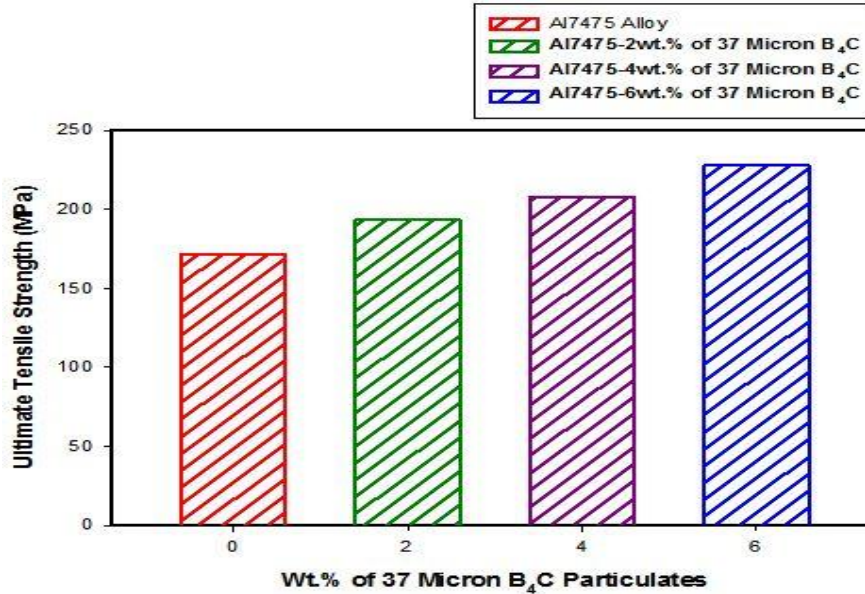


Figure 4: UTS of Al7475 alloy and 37 micron size B_4C composites

By noticing that the nature of the prepared composites is extremely dependent on the weight or volume division of the reinforcement leads to the increase in yield quality. Figure 5 showing the variation in yield strength (YS) of Al7475 alloy matrix with 2, 4 and 6 wt. % of micro B_4C particulates reinforced composites. It is noticed that by adding 2, 4 and 6 wt. % of micro B_4C particles the yield strength is improved from 149.1 MPa to 171.1 MPa, 184.9 MPa and 201.1 MPa respectively. The expansion in yield strength of the composite is clear because of the hard B_4C ceramic particles which contribute to the quality by delectating the aluminum network and bringing about more quality resistance of the composite against the connected ductile load [14]. On account of micro particle strengthened composites, the uniformly distributed hard ceramic particles in the grid make limitation till the plastic stream, in this way giving upgraded quality to the composite [15].

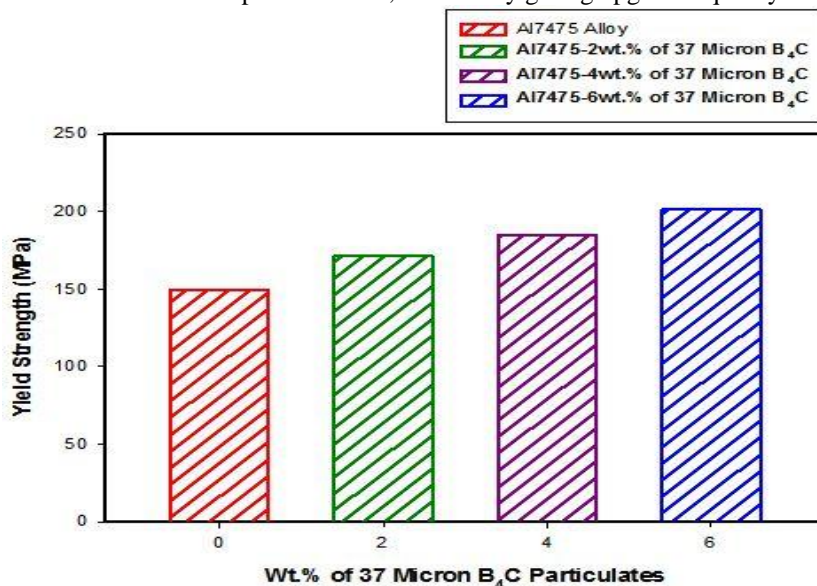


Figure 5: YS of Al7475 alloy and 37 micron size B_4C composites Percentage Elongation

Figure 6 representing the impact of 37 micron sized B_4C content on the ductility (elongation) of the composites and the flexibility of the composites reduces essentially with the 2, 4 and 6 wt. % B_4C prepared composites which can be noticed from the chart. This diminishing in rate prolongation in association with the matrix and reinforcement is a most commonly occurring disadvantage in particulate prepared metal matrix composites. The decreased malleability in micro composites can be attributed to the closeness of B_4C ceramic particulates which may get broke by stirring process and have sharp corners that make the composites distorted to limited part initiate and increase [16]. The delicate impact that happens because of the contact of the hard particles bringing on expanded locality stretch focus locales may like manner be the reason.

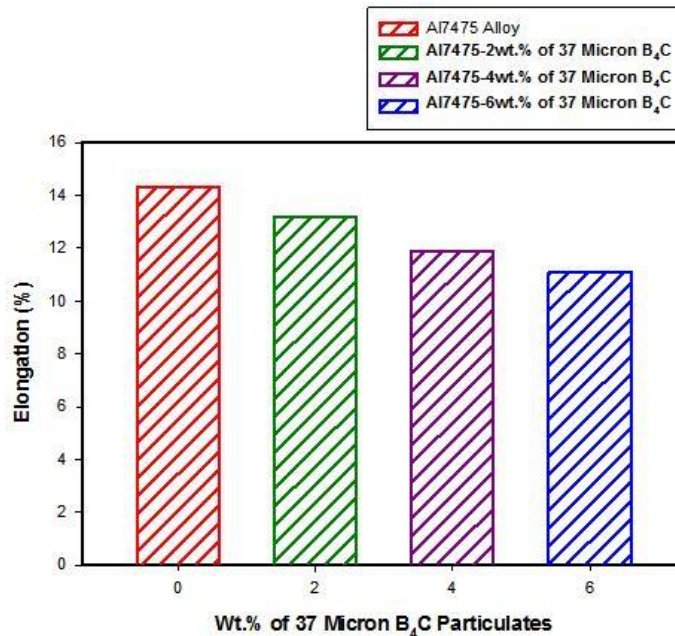


Figure 6: Percentage elongation of Al7475 alloy and 37micron B_4C composites

IV. CONCLUSIONS

In this research, by using stir casting fabrication technique the 37 micron B_4C /Al7475composites have been fabricated by considering 2, 4 and 6 wt. % of reinforcement. The microstructures, mechanical properties like hardness, ultimate tensile strength, and yield strength and percentage elongation behavior of prepared samples are studied as per ASTM standards. The matrix is almost free from pores in as cast alloy and uniformly distributed of micron particles in the prepared composite, which is evident from SEM microphotographs. The EDS analysis confirms the presence of B_4C particles in the Al alloy matrix. Compared to unreinforced material the mechanical properties of Al7475-2, 4 and 6 wt. % 37 micron sized B_4C composite are superior and enhanced. Further, as weight percentage of B_4C particulates increased from 2 to 6 wt.% in the Al alloy matrix, the ductility decreased.

REFERENCES

1. M. Kok, Production and mechanical properties of Al_2O_3 particle reinforced 2024 aluminium alloy composites. Journal of Materials Processing Technology 161, 381-387, 2005.
2. Ramesh C. S., Anwar Khan A. R., Ravikumar N., Savanprabhu P., Prediction of wear co-efficient of Al6061-TiO₂ composites. Wear 259, 602-608, 2005.
3. K. Umanath, K. Palanikumar, S. T. Selvamani, Analysis of dry sliding wear behavior of Al6061-SiC - Al_2O_3 hybrid metal matrix composites. Composites Part B 53, 159-168, 2013.
4. G. Chandramohan, S. Basavarajappa, J. Paulo Davim, Some studies on drilling of hybrid metal matrix composites based on Taguchi Technique. Journal of Materials Processing Technology 196, 332-338, 2003
5. K. H. W. Seah, S. C. Sharma, B. M. Girish, Effect of artificial aging on the hardness of cast ZA-27/Graphite particulate composites. Materials and Design Vol. 16, No. 6, 337, 1995.
6. S. A. Sajjadi, H. R. Ezatpour, M. Torabi, "Comparison of microstructure and mechanical properties of A356 aluminium alloy- Al_2O_3 composites fabricated by stir and compo casting processes", Materials and Design, 34, 2012, pp. 106-11.

7. Ranjith Bauri, M. K. Surappa, "Processing and properties of Al-Li-SiCp composites", Science and Technology of Advanced Materials, 8, 2007, pp. 494-502.
8. G. B. Veeresh Kumar, C.S.P. Rao, N. Selvaraj, "Studies on mechanical and dry sliding wear of Al6061-SiC composites", Composites Part B, 43, 2012, pp. 1185-1191.
9. J. Hashim, L. Looney, M. S. J. Hashmi, "Particles distribution in cast metal matrix composites part-I", Journal of Materials Processing Technology, 123, 2002, pp. 251-257.
10. R. K Everest, R. J. Arsenault, "Metal Matrix Composites: Processing and Interfaces", 1991.
11. B. Vijaya Ramnath, C. Elanchezhian, M. Jaivignesh, S. Rajesh, C. Parswajinan, "Evaluation of mechanical properties of aluminium alloy –alumina-boron carbide metal matrix composites", Materials and Design, 58, 2014, pp. 332-338.
12. Srimant Kumar Mishra, Sandyarani Biswas, Alok Satapathy, "A study on processing, characterization and erosion wear behaviour of silicon carbide particle filled ZA 27 metal matrix composites", Materials and Design, 55, 2014, pp. 958-965.
13. A. Baradeswaran, A. Elaya Perumal, "Study on mechanical and wear properties of Al 7075-Al₂O₃-graphite hybrid composites", Composites Part B, 56, 2014, pp. 464-471.
14. Madeva Nagal, Shivananda Kalgudi, Virupaxi Auradi, Shivaputrappa Kori, "Mechanical characterization of ceramic nano B₄C-Al2618 alloy composites synthesized by semi solid processing", Transactions of the Indian Ceramic Society, Vol.77, No.3, pp. 1-4, 2018.
15. T H Manjunatha, Y Basavaraj, Madeva Nagal, V Venkataramana, "Investigations on mechanical behavior of Al7075-nano B₄C composites", IOP Conf. Series: Materials Science and Engineering, 376, 012091, 2018.
16. B Adaveesh, Raghukumar J, Madeva Nagal, "Investigations on wear behavior of micro B₄C particulates reinforced Al7010 alloy composites," IOP Conference Series: Materials Science and Engineering, 310, 012155, 2018.